

TRANSIENT MULTIPHASE FLOW PHENOMENA AND DEFECT FORMATION IN STEEL CONTINUOUS CASTING

Allocation: Illinois/100 Knh

PI: Brian G. Thomas^{1,2}

Co-PIs: Seong-Mook Cho¹, Surya Pratap Vanka¹, Hyunjin Yang¹, Matthew Zappulla², Ahmed Taha³, Seid Koric^{1,3}

¹University of Illinois at Urbana-Champaign

²Colorado School of Mines

³National Center for Supercomputing Applications

EXECUTIVE SUMMARY

The objective of this project is to develop computational models to simulate transient multiphase flows and related phenomena, to apply them to gain an improved fundamental understanding of defect formation in continuous steel casting, and to find ways to further improve the process. Large-Eddy Simulations (LES) coupled with a Volume of Fluid (VOF) model were applied to track transient motion of the liquid mold flux/molten steel interface and slag entrainment into the molten steel pool during steady state continuous casting. In addition, the transport of argon bubbles in the molten steel and their capture into the solidifying steel shell were simulated using LES simulations coupled with a Lagrangian Discrete Phase Model for particle transport and particle capture criteria. Furthermore, the LES models were validated with facility measurements and applied to investigate optimal process conditions for the nozzle port angle, submergence depth of the nozzle, and Electro-Magnetic Braking (EMBr) field strength. These simulations on Blue Waters reveal deeper insights into defect formation during the continuous casting of steel and have enabled improved operation.

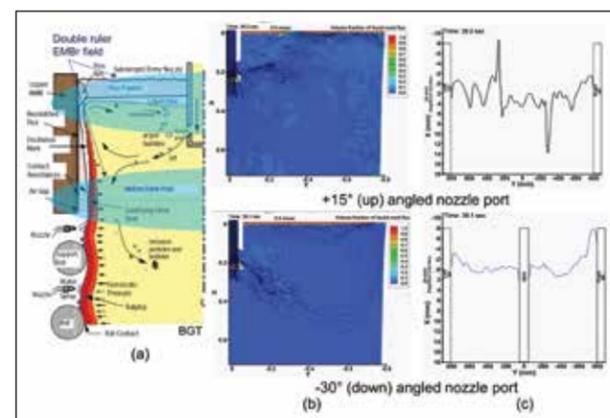


Figure 1: (a) Schematic of multiphase flow phenomena in the steel continuous-casting mold and Effect of nozzle port angle on (b) mold flow patterns, including motion of the top liquid mold flux layer, and (c) level variations at the liquid mold flux/molten steel interface in the meniscus region.

RESEARCH CHALLENGE

Continuous casting is the most widely employed solidification-process for steel manufacturing in the world [1], so even small improvements in this important process can lead to large benefits. Most defects in final products are related to transient multiphase flow phenomena in the mold region of the process (Fig. 1(a)). Severe instability at the liquid mold flux/molten steel interface can entrain some of the liquid mold flux (added on top of the molten steel pool in the mold to prevent steel oxidation) into the molten steel [2]. In addition, argon gas bubbles, injected to prevent nozzle clogging [3], can be trapped by the solidifying steel shell in the mold. To reduce these problems, transient multiphase flow phenomena should be understood, and process conditions should be optimized to reduce defect formation during continuous casting.

In this year's project, LES of several different important aspects of multiphase flow were performed to quantify the transient liquid mold flux/molten steel interface, transport of argon gas bubbles, and bubble capture into the steel shell in the mold during nominally steady continuous casting of steel slabs for different process conditions. The modeling results have been validated with plant measurements and applied to find optimal process conditions, including nozzle port angle, nozzle submergence depth, and EMBr field strength.

METHODS & CODES

LES coupled with VOF were applied to model transient molten steel flow and to track the liquid mold flux/molten steel interface. These models were implemented into the commercial package ANSYS Fluent on Blue Waters (BW) XE nodes. To calculate bubble transport and capture into solidifying steel shells with and without EMBr, LES coupled with Lagrangian particle capture (based on a force balance on each particle at the solidification front) [5] and MagnetoHydroDynamics models [8] using the GPU-based in-house code CUFLOW were employed on BW XK nodes.

RESULTS & IMPACT

Turbulent swirl flow from the upward-angled nozzle ports produces jet wobbling in the mold [4]. Sometimes, the jet impinges onto the liquid mold flux/molten steel interface and drags some of the liquid mold flux into the steel pool, resulting

in slag entrainment, as shown in Fig. 1(b). Most of the entrained slag becomes entrapped into the solidifying steel shell to form defects. Calculated interface instability reveals level variations greater than ~20 mm, especially at the meniscus region around its perimeter (Fig. 1(c)). These severe level instabilities can cause the liquid mold flux to touch the solidifying steel shell, and to be captured into the steel shell via meniscus hooks. However, the jet flow from the downward-angled nozzle ports with well-optimized casting conditions makes a classic double-roll pattern with less jet wobbling, resulting in better stability of the surface level and velocity in the mold. Velocity variations are smaller and the interface shows only ~2 mm fluctuations, so slag entrapment defects are drastically reduced.

Argon bubble motion is affected by turbulent jet flow in the mold, as shown in Fig. 2(a). Most bubbles larger than 3-mm in diameter float up toward the top surface due to their large buoyancy. On the other hand, small bubbles move along with the jet flow and easily reach the narrow face to be carried deep into the mold cavity. Many of the small bubbles move between the dendrites to be captured into the steel, especially without EMBr. However, EMBr slows and deflects the jet flow [6–7], so more bubbles float upward near the nozzle and fewer bubbles are transported to the narrow face and deep into the mold. As shown in Fig. 2(b), the bubble capture rate increases with time (until ~15-18 sec after gas injection for EMBr off and ~15 sec for EMBr on, because the jet flow path is shorter with EMBr). Then, after the flow has stabilized at nominally steady casting, EMBr is observed to reduce bubble entrapment significantly.

Parametric studies with these multiphase LES models have enabled better understanding of the complex multiphysics phenomena related to defect formation, including slag entrainment, inclusion and bubble transport, and capture. This has led to suggestions of nozzle geometry/casting condition combinations that lead to fewer defects, and, consequently, to significant savings to the steel plants.

WHY BLUE WATERS

Blue Waters enabled high-resolution multiphase flow simulations of the continuous caster needed for accurate predictions. In particular, the transient transport of small volume secondary-phases (entrained liquid mold slag and argon bubbles) in the turbulent flow require very small cells (~1 mm³) in a huge domain, and simulations of over 50-seconds flow time (with 0.001-second time steps). Furthermore, Blue Waters resources (both ANSYS Fluent HPC on XE nodes and our in-house multi-GPU code CUFLOW on XK nodes) showed speed-up breakthroughs (e.g., over 3000x with ANSYS Fluent HPC on BW) needed to provide this modeling capability for the steel continuous casting process.

PUBLICATIONS AND DATA SETS

Cho, S.-M., et al., Effect of Nozzle Port Angle on Transient Mold Flow, Surface Level, and Heat Transfer in Steel Caster. *CCC Annual Report*, Golden, Colo., August 16–18, 2016.

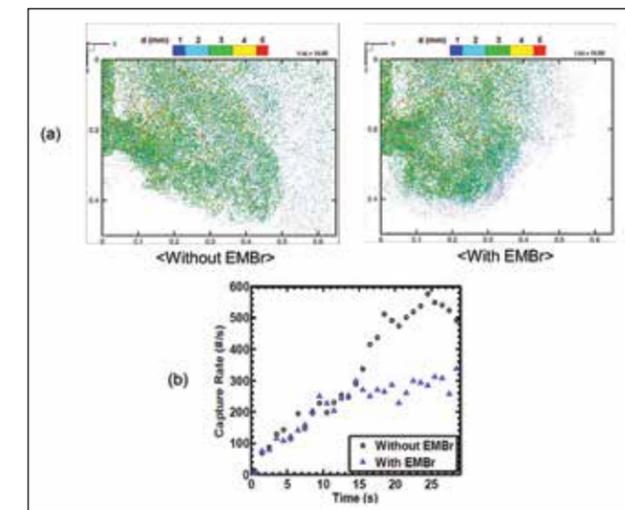


Figure 2: Effect of EMBr on (a) instantaneous argon bubble distributions and (b) bubble capture rate in the mold.

Jin, K., P. Kumar, S. P. Vanka, and B.G. Thomas, Rise of an argon bubble in liquid steel in the presence of a transverse magnetic field. *Physics of Fluids*, 28:9 (2016), DOI: 10.1063/1.4961561.

Jin, K., S. P. Vanka, R. K. Agarwal, and B. G. Thomas, GPU Accelerated Simulations of Three-Dimensional Flow of Power-law Fluids in a Driven Cube. *Int. J. Computational Fluid Mechanics*, 31:1 (2017), pp. 1029–10257. DOI 10.1080/10618562.2016.1270449.

Jin, K., S. P. Vanka, and B. G. Thomas, Large Eddy Simulation of the Effects of EMBr and SEN Submerged Depth on Turbulent Flow in the Mold Region of a Steel Caster. *Metallurgical and Materials Transactions B*, 48:1 (2016), pp. 162–178, DOI: 10.1007/s11663-016-0801-z.

Jin, K., S. P. Vanka, and B.G. Thomas, Large Eddy Simulations of Argon Bubble Transport and Capture in Mold Region of a Continuous Steel Caster. *Proc. TFEC2017*, Las Vegas, Nev., April 2–5, 2017.